



**THREE-DIMENSIONAL NONLINEAR FINITE ELEMENT ANALYSIS
ON THE SHEAR STRENGTH OF RC INTERIOR BEAM-COLUMN JOINTS
WITH ULTRA HIGH-STRENGTH MATERIALS**

T. KASHIWAZAKI and H. NOGUCHI

Department of Architecture, Faculty of Engineering, Chiba University,
1-33 Yayoi-cho, Inage-ku, Chiba-City, 263 Japan

ABSTRACT

Reinforced concrete (RC) interior beam-column joints with ultra high-strength materials were analyzed using three-dimensional (3-D) nonlinear finite element method (FEM). These specimens with concrete compressive strength of 100 MPa and the yield strength of longitudinal bars of 685 MPa were tested. The specimen OKJ3 of joint shear failure type was a plane interior joint, and the specimen I2 of beam flexural failure type was a 3-D interior joint with transverse beams.

Though the analytical initial stiffness was higher than experimental one, the analytical results gave a good agreement with the test results on the maximum story shear forces, the failure mode and the strain distributions of beam longitudinal bars.

KEYWORDS

Reinforced concrete; high-strength materials; beam-column joints; shear strength; FEM analysis.

INTRODUCTION

Interior beam-column joints in a reinforced concrete (RC) building are subjected to two-directional forces during an earthquake. In such interior beam-column joints, confined concrete in the joint results in the triaxial stress condition. It is also recognized that interior beam-column joints are confined by column axial force, joint lateral reinforcement, transverse beams and slabs. It is not desirable for the joints to neglect the severe stress conditions subjected to two-directional shear forces.

Design Guidelines for Earthquake Resistant RC Buildings Based on Ultimate Strength Concept for normal strength materials published by Architectural Institute of Japan (Architectural Institute of Japan, 1990) (AIJ Guidelines) suggest that such a 3-D interior beam-column joint should be designed for the two principal directions independently. AIJ Guidelines are based on a few test results. It is not so rational to establish the guidelines for the joints without the analytical understandings of the joint shear resistance mechanisms.

In this study, a plane RC interior beam-column joint without transverse beams and slabs, and a 3-D RC interior beam-column joint with transverse beams using ultra high-strength materials were analyzed using 3-D nonlinear finite element method (FEM) in order to clarify the shear resistance mechanisms of the joints and establish the rational design method of the joints.

Comparing the analytical results with the test results, restoring force characteristics, deformation, distributions of the beam longitudinal bars through a joint and internal stress flow along the joint were discussed.

OUTLINE OF FEM ANALYSIS

Reference Specimen for 3-D FEM Analysis

Specimens OKJ3 (Kashiwazaki *et al.*, 1991) and I2 (Lee *et al.*, 1992) were selected as the references for this study. Specimens OKJ3 and I2 were interior beam-column joints with ultra high-strength materials. As for specimen OKJ3 of the plane joint without transverse beams, joint shear failure occurred before beam flexural yielding. But as for specimen I2 of the 3-D joint with transverse beams, beam flexural failure before joint shear failure occurred in the test.

The properties of specimens OKJ3 and I2 are shown in Tables 1 and 2. The reinforcement arrangement of specimens OKJ3 and I2 are shown in Figs 1 and 2, respectively.

Specimen OKJ3 was tested by the authors. An one-third scaled specimen OKJ3 had a interstory height of 147 cm and a beam span of 270 cm. The dimensions of beams and columns were 200 x 300 mm and 300 x 300 mm, respectively. The beam was reinforced by bars of diameter 13 mm with a yielding stress of 717 MPa, and the compressive strength of concrete was 107 MPa. The joint lateral reinforcement ratio was 0.54 %. Reversed cyclic loads were applied to two beam-ends of specimen OKJ3 under each story drift angle of 1/200, 1/100, 1/50, 1/33 and 1/25 rad.. A constant axial load of 85 tons was applied to the column (axial stress $\sigma_0 = 0.1\sigma_B$, σ_B : concrete compressive strength).

Specimen I2 was tested by Lee *et al.* of the University of Tokyo. As shown in Fig. 2, specimen I2 had the same interstory height, beam spans and dimensions of beams and columns with specimen OKJ3. The beam was reinforced by bars of diameter 16 mm with a yielding stress of 798 MPa, and the compressive strength of concrete was 99 MPa, as shown in Tables 1 and 2. The joint lateral reinforcement ratio was 0.39 %. Three dimensional reversed cyclic loads were applied to the top of the column until the story drift angle of 1/25 rad. . A constant axial load of 32.5 tons was applied to the top of the column.

Table 1 Properties of specimen

Specimen		Two-Dimensional OKJ3	Three-Dimensional I2
Beam	Top Bars	10-D13	8-D16
	Bottom Bars	10-D13	8-D16
	Stirrups	2-D6 @50, $p_w=0.63(\%)$	2-U6.4 @35, $p_w=0.86(\%)$
Column	Total Bars	22-D13	16-D19
	Hoops	2-D6 @40, $p_w=0.53(\%)$	2-U6.4 @40, $p_w=0.50(\%)$
Joint	Hoops	4-D6 × 3sets @50 $p_w=0.54(\%)$	4-φ6 × 2sets@30 $p_w=0.39(\%)$

Table 2 Material properties

a) Concrete (unit in MPa and μ)

Specimen	Two-Dimensional OKJ3	Three-Dimensional I2
Secant Modulus	43300	39200
Compressive Strength	107	99
Strain at Comp. Strength	2860	2752
Splitting Strength	6.0	4.2

b) Reinforcement (unit in MPa and μ)

Specimen	Two-Dimensional OKJ3			Three-Dimensional I2		
	D6	D13	D16	D19	U6.4	φ6
Young's Modulus	182000	186000	182000	181000	186000	186000
Yield Strength	955	717	798	746	1307	356
Strain at Yielding	7340	5870				
Max. Strength	1140	766	859	806	1397	431

Concrete : Concrete was represented by 8-node solid elements. Concrete was assumed as orthotropic hypoelastic model based on the equivalent uniaxial strain concept modified by Murray et al. for the 3-D FEM analysis. The failure was judged by the five parameter criterion which was added two parameters to the three parameter criterion proposed by Willam and Warnke. The five parameters were decided using the panel experiment by Kupfer.

Fafitis-Shah model (Fafitis *et al.*, 1985) was used for the ascending compressive stress-strain relationships (1), as shown in Fig. 5, because the stress-strain relationships of high-strength concrete show linear just before the compressive strength.

$$\sigma_c = \sigma_B [1 - (1 - \epsilon_c / \epsilon_B)^A], A = E_c \cdot \epsilon_B / \sigma_B \tag{1}$$

σ_c : stress in concrete (kgf/cm²)
 σ_B : compressive strength of concrete (kgf/cm²)
 ϵ_c : strain in concrete (dimension-less)
 ϵ_B : strain in concrete at the compressive strength (dimension-less)
 E_c : initial stiffness of concrete (kgf/cm²)

Confined effect by lateral reinforcement on the compressive descending stress-strain relationships were represented by Kent-Park model (Kent *et al.*, 1971). Poisson's ratio of concrete was modeled as a function of compressive strain proposed by Murray. Cracks in concrete elements were represented by the smeared crack model. After cracking, tension cut-off was assumed, and the stiffness normal to a crack direction was set to be zero. The reduction factor of concrete compressive strength of cracked concrete proposed by Izhuka and Noguchi (Izhuka *et al.*, 1992) was used. This Izhuka-Noguchi model was derived from the test results of cracked RC panels with from normal to high strength materials.

Reinforcement : The longitudinal and lateral reinforcement in columns and beams was assumed to be a linear element. The stress-strain relationships of the longitudinal and lateral reinforcement were assumed to be bilinear and trilinear, respectively.

Bond : Bond between the longitudinal reinforcement and concrete was assumed as perfect bond. The slippage of beam longitudinal reinforcement through a joint was not considered.

Test results were used for the mechanical properties of concrete and reinforcing bars in the analysis.

ANALYTICAL RESULTS

Plane Interior Beam-Column Joint (OKJ3)

Restoring Force Characteristics. The analytical story shear force-story displacement relationships of a plane interior beam-column joint, specimen OKJ3 are shown in Fig. 6 as compared with the test results. The analytical initial stiffness was higher than the experimental one up to the story drift angle (Rs) of 1/200 rad.. As for the maximum story shear force (Ps), the analytical results (Ps = 33.5 tons) were higher than test results (Ps = 29.9 tons) about 10 percent. The yielding of beam longitudinal reinforcement did not occur in this analysis until the maximum story shear forces, and a few concrete elements in the joint reached strain softening area over concrete compressive strength at the maximum story shear force. It was recognized that the joint shear failure before beam flexural yielding (J failure) occurred in the joint of specimen OKJ3 similarly to the experiment.

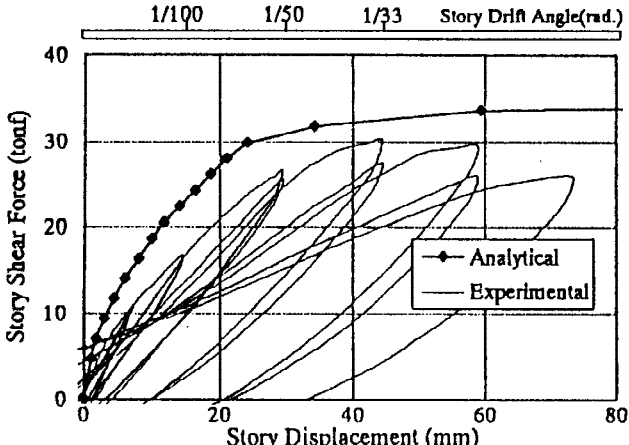


Fig. 6 Story shear force-story displacement relationships (OKJ3)

It was recognized that the joint shear failure before beam flexural yielding (J failure) occurred in the joint of specimen OKJ3 similarly to the experiment.

CONCLUSIONS

In order to understand the shear resistance mechanisms and the shear capacity of RC interior beam-column joints with ultra high-strength materials, two specimens of a plane joint with the joint shear failure type and a 3-D joint with the beam flexural failure type were analyzed using a nonlinear 3-D FEM analysis. From the detailed investigations of the FEM analytical results in comparison with the test results, the following conclusions were obtained.

Though the analytical initial stiffness of restoring force was higher than experimental one, the analytical results gave a good agreement with the test results on the maximum story shear forces, the failure mode and the strain distributions of the beam longitudinal bars.

Concrete stresses in the main diagonal strut of a joint panel was about 40 percent of the concrete uniaxial compressive strength in both cases of the plane and the 3-D joint. In the case of the plane joint, joint shear failure before beam flexural yielding occurred. On the other hand, in the case of the 3-D joint, joint shear failure did not occur. Accordingly, it is considered that the joint shear strength is increased by the joint confinement effect of transverse beams.

In the future, in order to develop the rational design method of joints, it is necessary to investigate the joint shear resistance mechanisms using the results of the parametric 3-D FEM analysis including the variations of the concrete compressive strength, joint lateral reinforcement, column axial load, transverse beams and floor slabs.

ACKNOWLEDGMENTS

The work reported in this paper was sponsored by Grant-in-Aid for Co-operative Research (No.04302049, Representative Researcher: Professor H. Noguchi, Chiba University) and Encouragement of Young Scientists (No.06750599, Representative Researcher: Research Associate T. Kashiwazaki, Chiba University) of the Ministry of Education, Science, Sports and Culture of Japanese Government.

The authors wish to express our gratitudes to members of the co-operative research, Associate Professor K. Kitayama and Research Associate S. Lee of Tokyo Metropolitan University for their useful suggestions and offers of the detailed test data.

REFERENCES

- Architectural Institute of Japan (1990). *Design Guidelines for Earthquake Resistant Reinforced Concrete Buildings Based on Ultimate Strength Concept*. (in Japanese)
- Fafitis, A. and S. P. Shah (1985). Lateral Reinforcement for High-Strength Concrete Columns. *ACI, SP - 87*, pp. 213-232.
- Ihzuka, T. and H. Noguchi (1992). Nonlinear Finite Element Analysis of Reinforced Concrete Members with Normal to High Strength Materials. *Proceedings of the Japan Concrete Institute, Vol. 14, No. 2*, pp. 9-14, (in Japanese).
- Kashiwazaki, T. and H. Noguchi (1991). Experimental Study on the Shear Performance of R/C Interior Beam-Column Joints with Ultra High-Strength Materials. *Proceedings of the Japan Concrete Institute, Vol. 13, No. 2*, pp. 475-478, (in Japanese).
- Kashiwazaki, T. and H. Noguchi (1994). Nonlinear Finite Element Analysis on Shear and Bond of R/C Interior Column-Beam Joints with Ultra High-Strength Materials. *Proceedings of the Japan Concrete Institute, Vol. 16, No. 2*, pp. 741-744, (in Japanese).
- Kent, D. C. and R. Park (1971). Flexural Members with Confined Concrete. *Journal of the Structural Division, Proceedings of the ASCE, ST7*, pp. 1969-1990.

- Lee, S., K. Kitayama, S. Otani and H. Aoyama (1992). Shear Strength of Reinforced Concrete Interior Beam-Column Joints Using High-Strength Materials. *Proceedings of the Japan Concrete Institute*, Vol. **14**, No. **2**, pp. 379-384, (in Japanese).
- Uchida, K., A. Amemiya and H. Noguchi (1992). Three-dimensional Nonlinear Finite Element Analysis for Reinforced Concrete Members. *Summaries of Technical Papers of Annual Meeting of Architectural Institute of Japan*, **Structures II**, pp. 1061-1064. (in Japanese)
- Yonezawa, K. and H. Noguchi (1994). Study on Shear Strength of Beam-Column Joints of Mixed Structure by FEM Analysis (Part 1 and 2). *Summaries of Technical Papers of Annual Meeting of Architectural Institute of Japan*, **Structures II**, pp.1623-1626, (in Japanese)